

AD

AD 691727

CCL REPORT NO. 268

FINAL REPORT


STUDY OF LONG TERM PACKAGING OF ETHYLENE GLYCOL ANTIFREEZE

BY

JAMES H. CONLEY

JULY 1969

Reproduction of
CLEARINGHOUSE
for Federal Government Technical
Information Springfield, VA 22151

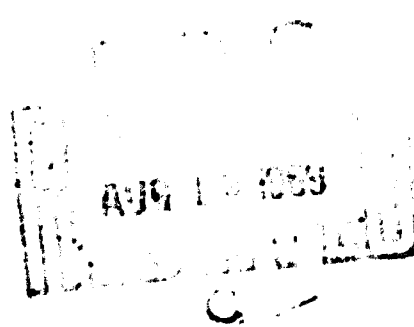

THIS DOCUMENT HAS BEEN APPROVED FOR PUBLIC RELEASE
AND SALE; ITS DISTRIBUTION IS UNLIMITED

U. S. ARMY ABERDEEN RESEARCH & DEVELOPMENT CENTER
COATING & CHEMICAL LABORATORY

Aberdeen Proving Ground
Maryland

COLOR ILLUSTRATIONS REPRODUCED
IN BLACK AND WHITE

ACCESSION NO.	
CESTI	WORKS EDITION <input checked="" type="checkbox"/>
DDC	REVISION EDITION <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
DIST.	AVAIL. AND SPECIAL
/	

DDC AVAILABILITY NOTICE

Qualified requesters may obtain copies of this report from Defense Documentation Center, Cameron Station, Alexandria, Virginia 22314.

THE FINDINGS IN THIS REPORT ARE NOT TO BE CONSTRUED AS AN OFFICIAL DEPARTMENT OF THE ARMY POSITION, UNLESS SO DESIGNATED BY OTHER AUTHORIZED DOCUMENTS.

DESTROY THIS REPORT WHEN IT IS NO LONGER NEEDED. DO NOT RETURN IT TO THE ORIGINATOR.

**Best
Available
Copy**

UNCLASSIFIED

CCL REPORT NO. 268

FINAL REPORT

STUDY OF LONG TERM PACKAGING OF ETHYLENE GLYCOL ANTIFREEZE

BY

JAMES H. CONLEY

JULY 1969

AMCMS CODE NO. 5025.11.803

DEPARTMENT OF THE ARMY PROJECT NO.
1G062105A109

U.S. ARMY ABERDEEN RESEARCH & DEVELOPMENT CENTER
COATING AND CHEMICAL LABORATORY
ABERDEEN PROVING GROUND
MARYLAND

THIS DOCUMENT HAS BEEN APPROVED FOR PUBLIC RELEASE
AND SALE; ITS DISTRIBUTION IS UNLIMITED

UNCLASSIFIED

i

COLOR ILLUSTRATIONS REPRODUCED
IN BLACK AND WHITE

ABSTRACT

The object of this study was to investigate conditions which would effect long term packaging of ethylene glycol antifreeze. Factors investigated were pH, dilution, different inhibitor systems and different metals.

Aluminum and tin-coated steel panels were partially immersed in ethylene glycol solutions contained in test jars at room temperatures for a period of ten years. Inhibitors used in this study included borax, borax/glycol condensate, mercaptobenzothiazole, and the sodium salt of mercaptobenzothiazole. pH values ranging from 6 to 10.5 were used. Test solutions contained 0%, 3% and 66-2/3% water.

No system tested was adequate for 10 years storage. All systems exhibited corrosion in the liquid phase and/or the vapor phase.

TABLE OF CONTENTS

	<u>Page No.</u>
TITLE PAGE	i
ABSTRACT	ii
INTRODUCTION	1
DETAILS OF TEST	1 - 2
RESULTS OF TEST	2 - 3
REFERENCES	3 - 4
DISTRIBUTION LIST	5 - 6
APPENDIX A	7
Tables 1 - 11	7 - 11
APPENDIX B	12
Photographs 1 - 35	13 - 20
DD FORM 1473	21

I. INTRODUCTION

Coating & Chemical Laboratory was directed by Army Materiel Command to investigate improved antifreeze compounds.

Federal Specification 0-A-548, Type I antifreeze which is specified for Army use in TB-750-651 is composed of undiluted ethylene glycol with borax as an inhibitor. As packaged it has an acidic pH (below 7.0) and tends to cause corrosion of tin containers in long term storage. This material is used in conjunction with 0-1-490a, Inhibitor, Corrosion, Liquid Cooling System. One of the constituents of 0-1-490a is mercaptobenzothiazole (MBT) which greatly enhances the inhibitive properties of borax in ethylene glycol mixtures which have been diluted for vehicle use. However, chemically, MBT is an acid, and was found to rapidly corrode the tin containers when incorporated directly into undiluted 0-A-548 antifreeze packages. The Army, therefore, uses a two package antifreeze system, which is logistically undesirable.

This study was initiated primarily to study conditions which might permit the incorporation of 0-A-548 and 0-1-490a into a one package antifreeze system. Preliminary data on this study were presented in CCL Report Nos. 86 and 100. These data showed that under specified conditions ethylene glycol could be packaged with MBT and stored for short periods in both aluminum and tin coated steel containers.

This present report contains data derived from the study since the two year inspection.

II. DETAILS OF TEST

A. Test Panels.

Aluminum (alloy 2024) panels 2-1/2" by 3", were prepared by abrading with 320A carborundum paper and steel wool (00 Grade), rinsing with hot ethyl alcohol and drying in an oven at 210°F.

Tin coated steel panels, 2-1/2" x 3" were prepared by lightly abrading with steel wool (00 Grade), rinsing in hot ethyl alcohol and drying in an oven at 210°F. The edges of these panels were then dipped in a non-crystalline hydrocarbon wax so that steel edges would not be exposed.

B. Test Jars.

The glass jars used in the test were 14-1/2 ounce screw cap type, approximately 3" in diameter and 4" deep. The jars were closed with screw caps containing lacquered paper pulp liners.

C. Ethylene Glycol.

Ethylene glycol used in the tests was "purified" grade, Fisher Scientific Company. This glycol contained less than 0.5% water.

D. Inhibitors.

1. Borax - The borax used was sodium tetraborate, decahydrate, C.P. It analyzed 101%, calculated as borax, the excess percentage being due to the loss of water of hydration.

2. Borax-glycol condensate - This material was prepared in accordance with the procedure outlined in CCL Report No. 81. It analyzed $14.0 \pm 1.0\%$ sodium tetraborate (by weight).

3. Mercaptobenzothiazole - Eastman Kodak 2-mercaptobenzothiazole "practical" grade, was used.

4. Sodium salt of mercaptobenzothiazole - R. T. Vanderbilt's "NACAP", which is a 50% water solution of sodium mercaptobenzothiazole, was used in the tests in amounts corresponding to the quantity of MBT used.

E. Tests Conducted.

1. Test solutions - Thirty-five test solutions used in this study are listed in Tables I and II. A pH of 10.5 was attained by the addition of 5.0N aqueous sodium hydroxide.

2. Test procedures - Approximately 200 ml. of solution was placed in each jar. The metal test panel was approximately one half immersed. This permitted inspection of panels exposed to both the liquid phase and the vapor phase. The screw caps were firmly tightened and the jars stored on a shelf at room temperature.

3. Inspection - One set of duplicate panels were removed in two month intervals up to 8 months for inspections. The duplicate set of panels were left undisturbed for a total of 24 months storage and inspected. The panels were then placed back in the test jars and left undisturbed for a total of 10 years. The final inspection included in this study was made after 10 years storage.

III. RESULTS OF TEST

A. Effect of dilution on tin-coated steel.

Results of inspections up to 8 months and 2 years are included in CCL Report Nos. 86 and 100, respectively. Results in Table I and the photographs show all undiluted samples exhibit heavy corrosion both in the vapor phase and liquid phase. Tests with 97% glycol and 3% water

(Test Nos. 6 and 11) were better than the undiluted samples but were not as good as the tests with 66-2/3% water (Test Nos. 12 to 23A). This shows that dilution decreases corrosion on tin-coated steel.

B. Effect of dilution on aluminum.

Results of the effect of dilution on aluminum in Table II and the photographs show that dilution increased corrosion in nearly every case. One exception was noted with 2-1/4% borax-glycol condensate, 1/2% NACAP at pH 10.5.

C. Effect of pH.

Increasing the pH of undiluted glycol to 10.5 increased the vapor phase corrosion of aluminum in every case with only a slight difference in the liquid phase corrosion. Increasing the pH to 10.5 at 3% dilution decreased the corrosion of tin-coated steel but at 66-2/3% dilution the increased pH increased corrosion.

D. Comparison of borax-glycol condensate.

Borax-glycol condensate was slightly better than borax in 66-2/3% dilution low pH tests in the liquid phase and in the high pH tests with tin-coated steel. Borax was better than the condensate in the high pH test with 1/2% NACAP at 3% dilution (Table II, Test Nos. 27 and 28).

E. Comparison of MBT and its sodium salt.

The sodium salt of MBT (NACAP) was better than MBT in almost every case. In Test Nos. 8 and 11 with 97% glycol, 2-1/4% borax and 3% water at pH 10.5 the MBT was better than the sodium salt.

F. Best overall inhibitor combination.

In choosing a single inhibitor combination from this group which would be best on both metals, borax, MBT, and 3% water at pH 10.5 would be the best. At 66-2/3% dilution the condensate with NACAP at pH 10.5 is the best. Even these would not be considered satisfactory for long term storage due to the presence of some corrosion either in the vapor phase or the liquid phase. All corrosion is more severe after 10 years storage and in the same order as reported after 2 years storage.

IV. REFERENCES

1. Authority, AMC Program Directive.
2. Federal Specification 0-1-490, Inhibitor, Corrosion, Liquid Cooling System.

3. Federal Specification 0-A-548a, Antifreeze, Ethylene Glycol, Inhibited.
4. CCL Report No. 81, Development of an Operational Preservative Hydraulic Brake Fluid, August 1959.
5. CCL Report No. 86, Study of a Newly Developed Inhibitor for Ethylene Glycol in Storage, October 1959.
6. CCL Report No. 100, Storage of Ethylene Glycol with Various Inhibitors, 14 March 1961.

DISTRIBUTION LIST FOR AMCMS CODE NO. 5025.11.803

<u>Department of Defense</u>	<u>No. of Copies</u>
Defense Documentation Center Cameron Station Alexandria, Virginia 22314	20
<u>Department of the Army - Technical Service</u>	
Commanding General U. S. Army Materiel Command ATTN: AMCRD-GF Washington, D. C. 20315	1
Continental Army Command Department of the Army Fort Monroe, Virginia 23351	3
Commanding General U. S. Army Tank-Automotive Command ATTN: Mr. J. P. Jones Warren, Michigan 48090	1
Commanding Officer Frankford Arsenal ATTN: L7000-64-4 Library Philadelphia, Pennsylvania 19137	1 1
Commanding Officer U.S. Army Materials & Mechanics Research Center ATTN: Technical Information Center Watertown, Massachusetts 02172	2
Commanding Officer Yuma Proving Ground Arizona 85364	1
Commanding General U. S. Army Weapons Command ATTN: AMSWE-RDR Rock Island, Illinois 61200	2
Commanding Officer U. S. Army Chemical Research & Development Laboratories ATTN: Librarian Edgewood Arsenal, Maryland 21040	1

DISTRIBUTION LIST CONTINUED

	<u>No. of Copies</u>
Commanding Officer U. S. Army Mobility Equipment Research and Development Center ATTN: Technical Documents Center Fort Belvoir, Virginia 22060	2
Commanding Officer Rock Island Arsenal ATTN: Laboratory 9320 Rock Island, Illinois 61200	1
Commanding Officer U. S. Army Ballistic Research Laboratories ATTN: Mr. R. Eichelberger Mr. J. Sperrazza Aberdeen Proving Ground, Maryland 21005	1 1
Technical Library Aberdeen Proving Ground, Maryland 21005	2
Air Force Systems Command ATTN: STLO Bldg 314 Aberdeen Proving Ground, Maryland 21005	2
<u>Department of the Navy</u>	
Department of the Navy c/o Navy Liaison Aberdeen Proving Ground, Maryland 21005	1
Department of the Navy Chief, Bureau of Naval Weapons Washington, D. C. 20360	1
<u>Other Government Agencies</u>	
NASA Scientific and Technical Information Facility P. O. Box 33 College Park, Maryland 20740	3
Federal Aviation Administration 800 Independence Avenue S. W. ATTN: Administrative Standards Division (MS-110) Washington, D. C. 20590	2

APPENDIX A

TABLE I

Results of 10-Year Inspection Tin-Coated Steel Panels

Photo No.	Inhibitor Combination	Dilution, % water	Results	Solution Appearance
1	None pH 4.90	Undiluted	Very heavy vapor phase corrosion. Liquid phase full of holes.	Very rusty
2	2-1/2% Borax, pH 5.68	Undiluted	Mod-heavy vapor phase corrosion. Tin completely removed in liquid phase. Steel shows intergranular corrosion.	Very rusty
3	2-1/2% Borax-Glycol Condensate pH 5.55	Undiluted	Pitting in vapor phase. Heavy rusting at interface. Tin partially removed in liquid phase. Some intergranular corrosion.	Very rusty
4	2-1/4% Borax, 1/4% MBT, pH 5.65	Undiluted	Heavy vapor phase corrosion. Liquid phase black and pitted.	Very rusty
5	2-1/4% Borax-Glycol Condensate 1/4% MBT, pH 5.55	Undiluted	Heavy vapor phase corrosion. Liquid phase black and pitted.	Very rusty
6	None pH 5.35	3	Heavy vapor phase corrosion. Tin removed from panels in liquid phase. Steel perforated with holes.	Very rusty
7	2-1/4% Borax, 1/2% NACAP, pH 6.00	3	Very heavy vapor phase corrosion. Very heavy liquid phase corrosion.	Very rusty
8	2-1/4% Borax, 1/4% MBT, pH 10.5	3	Slight vapor phase corrosion. Liquid phase okay.	Trace of sediment
9	2-1/4% Borax-Glycol Condensate 1/4% MBT, pH 5.75	3	Very heavy vapor phase corrosion. Excessive pitting in liquid phase.	Very rusty (black)

TABLE 1 - (Continued)

Photo No.	Inhibitor Combination	Dilution, % water	Results	Solution Appearance
10	2-1/4% Borax-Glycol Condensate, 1/4% MBT, pH 10.5	3	Vapor phase stained. Tin completely removed in liquid phase. Steel shows intergranular corrosion.	Very slight yellow sediment.
11	2-1/2% Borax Condensate 1/2% NACAP, pH 10.5	3	Moderate vapor phase corrosion. Liquid phase coated with crystals but no evidence of pits.	Very slight sediment.
12	None pH 4.55	66-2/3	Very heavy vapor phase corrosion. Panel completely dissolved except under the wax in the liquid phase.	Very rusty
13	2-1/2% Borax pH 7.82	66-2/3	Slight vapor phase corrosion. Liquid phase okay.	Clear
14	2-1/2% Borax-Glycol Condensate, pH 7.85	66-2/3	Light scattered pitting. Liquid phase stained.	Clear
15	2-1/4% Borax, 1/4% MBT pH 7.72	66-2/3	Heavy vapor phase corrosion. Liquid phase stained and coated.	Yellow sediment
16	2-1/2% Borax pH 10.5	66-2/3	Scattered pitting. Filiform corrosion in liquid phase.	Clear
17	2-1/4% Borax, 1/4% MBT, pH 10.5	66-2/3	Very heavy vapor phase corrosion. Heavy pitting and rusting in liquid phase.	Rusty
17A	2-1/4% Borax 1/4% MBT pH 10.5	66-2/3	Very slight vapor phase corrosion. Tin completely removed in liquid phase. Steel show intergranular corrosion.	Slight sediment

TABLE I - (Continued)

Photo No.	Inhibitor Combination	Dilution, % water	Results	Solution Appearance
18	2-1/4% Borax-Glycol Condensate 1/4% MBT, pH 7.55	66-2/3	Very slight vapor phase corrosion. Tin completely removed in liquid phase. Steel shows intergranular corrosion.	Slight yellow sediment
19	2-1/4% Borax-Glycol Condensate 1/4% MBT	66-2/3	Vapor phase okay. Tin partly removed in liquid phase. Some intergranular corrosion.	Slight sediment (white)
20	2-1/4% Borax, 1/2% NACAP pH 7.88	66-2/3	Slight vapor phase corrosion. Slight corrosion and stains in liquid phase.	Heavy white sediment
21	2-1/4% Borax, 1/2% NACAP, pH 10.5	66-2/3	Slight vapor phase corrosion. Light etching with tin removed in one spot.	Very slight sediment
22	2-1/4% Borax-Glycol Condensate, 1/2% NACAP, pH 7.88	66-2/3	Very slight vapor phase corrosion. Moderate-heavy stain in liquid phase.	Heavy light yellow sediment
22A	2-1/4% Borax-Glycol, Condensate, 1/2% NACAP, pH 7.88	66-2/3	Slight vapor phase corrosion. Heavy corrosion at interface on one side. Liquid phase okay.	Moderate-Heavy yellow sediment
23	2-1/4% Borax-Glycol, Condensate, 1/2% NACAP, pH 10.5	66-2/3	Slight vapor phase corrosion. Light yellow stain in liquid phase. No pitting.	Very slight sediment
23A	2-1/4% Borax-Glycol, Condensate, 1/2% NACAP, pH 10.5	66-2/3	Very slight vapor phase corrosion pitting in liquid phase	Slight sediment

TABLE II


Results of 10 Year Inspection Aluminum Panels

Photo No.	Inhibitor Combination	Dilution, % water	Results	Solution Appearance
24	2-1/4% Borax, 1/4% MBT, pH 10.5	3	Heavy vapor phase corrosion. Moderate-heavy corrosion in liquid phase.	Moderate white sediment
25	2-1/4% Borax-Glycol, Condensate, 1/4% MBT, pH 10.5	3	Moderate vapor phase corrosion. Moderate corrosion in liquid phase.	Very slight sediment
26	2-1/4% Borax, 1/2% NACAP, pH 6.00	3	Moderate vapor phase corrosion. Light stain in liquid phase.	Moderate-Light yellow sediment
27	2-1/4% Borax, 1/2% NACAP, pH 10.5	3	Moderate vapor phase corrosion. Slight-moderate coating in liquid phase	Moderate sediment
28	2-1/4% Borax-Glycol, Condensate, 1/2% NACAP, pH 10.5	3	Moderate vapor phase corrosion. Heavy coating in liquid phase.	Slight sediment
29	2-1/4% Borax, 1/4% MBT, pH 7.72	66-2/3	Moderate-heavy vapor phase corrosion. Moderate-heavy coating in liquid phase.	Moderate white sediment
30	2-1/4% Borax, 1/4% MBT, pH 10.5	66-2/3	Moderate vapor phase corrosion. Heavy coating in liquid phase.	Slight-moderate white sediment
31	2-1/4% Borax-Glycol Condensate, 1/4% MBT, pH 10.5	66-2/3	Moderate vapor phase corrosion. Heavy liquid phase corrosion.	Slight sediment

TABLE II - (Continued)

<u>Photo No.</u>	<u>Inhibitor Combination</u>	<u>Dilution, % water</u>	<u>Results</u>	<u>Solution Appearance</u>
32	2-1/4% Borax, 1/2% NACAP, pH 7.88	66-2/3	Very slight vapor phase corrosion. Slight-moderate stain and pitting in liquid phase.	Moderate-heavy white sediment
33	2-1/4% Borax, 1/2% NACAP, pH 10.5	66-2/3	Moderate vapor phase corrosion. Light scattered pitting and stain in liquid phase.	Slight-moderate sediment
34	2-1/4% Borax-Glycol, Condensate, 1/2% NACAP, pH 7.60	66-2/3	Vapor phase okay. Light overall coating in liquid phase.	Moderate-light yellow sediment
35	2-1/4% Borax-Glycol, Condensate, 1/2% NACAP, pH 10.5	66-2/3	Slight vapor phase corrosion. Moderate pitting in liquid phase.	Very slight sediment

APPENDIX B

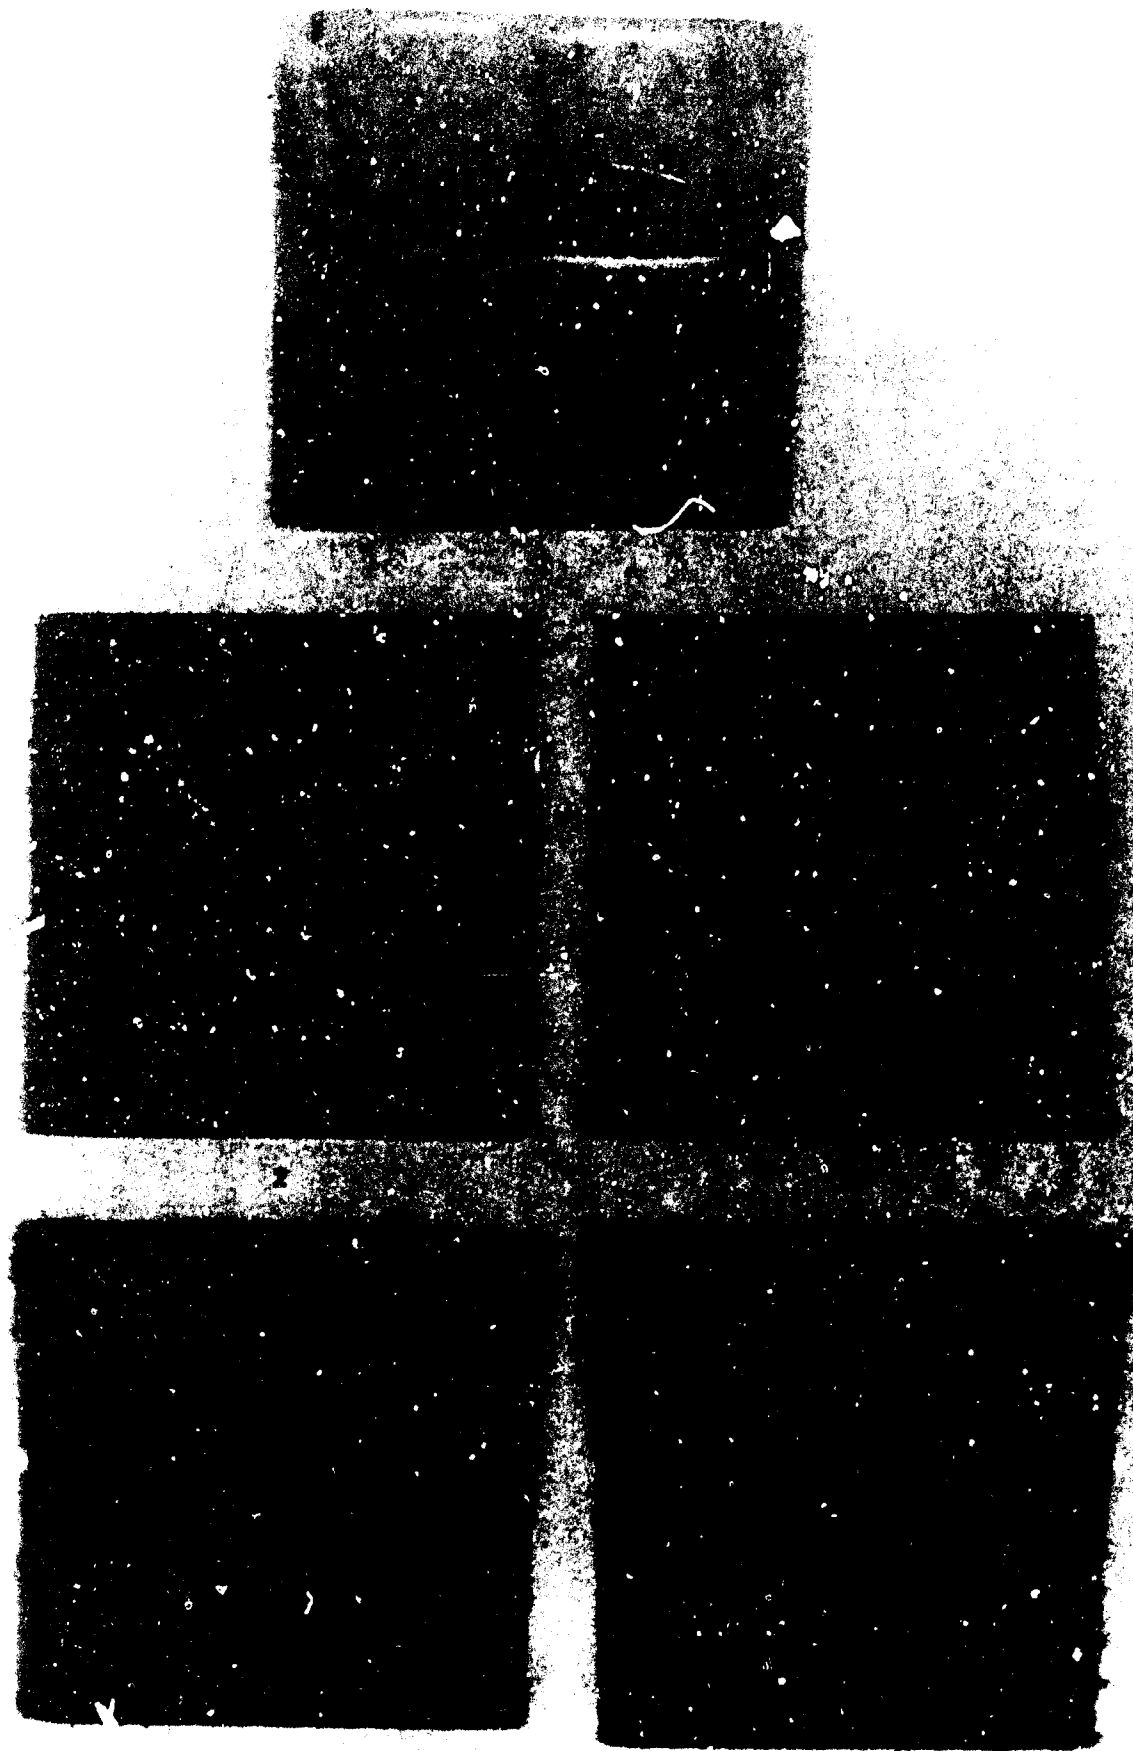


4

5

TIN COATED STEEL PANELS

Panels immersed in Undiluted Ethylene Glycol with various inhibitors

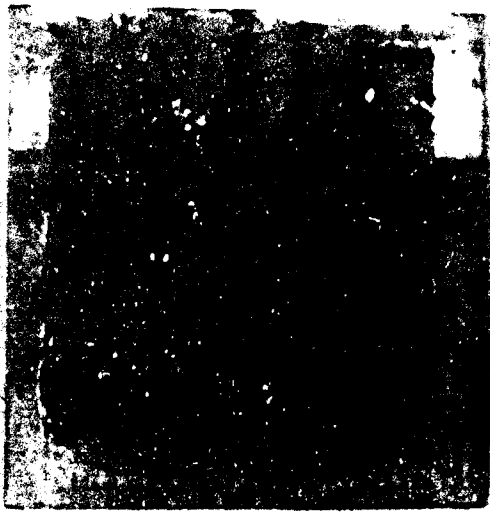

6




7



8



9

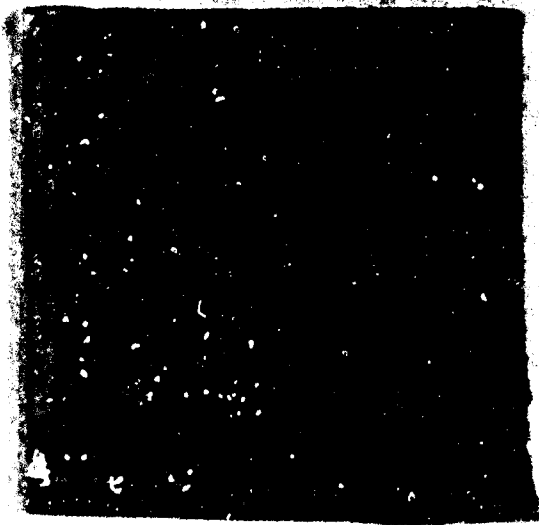




10



11

TIN COATED STEEL PANELS

Panels immersed in 97% Ethylene Glycol, 3% water, with various inhibitors

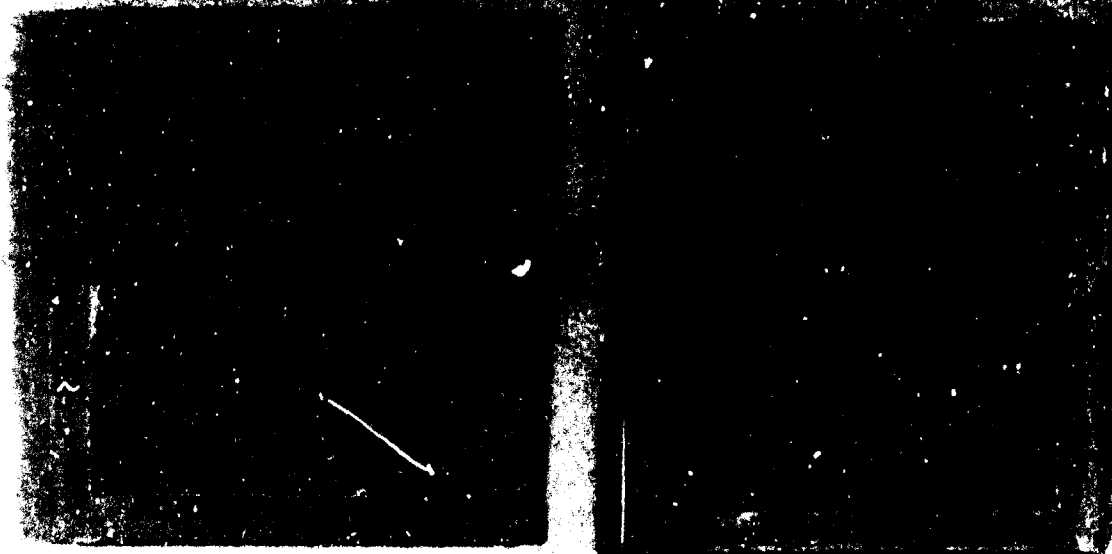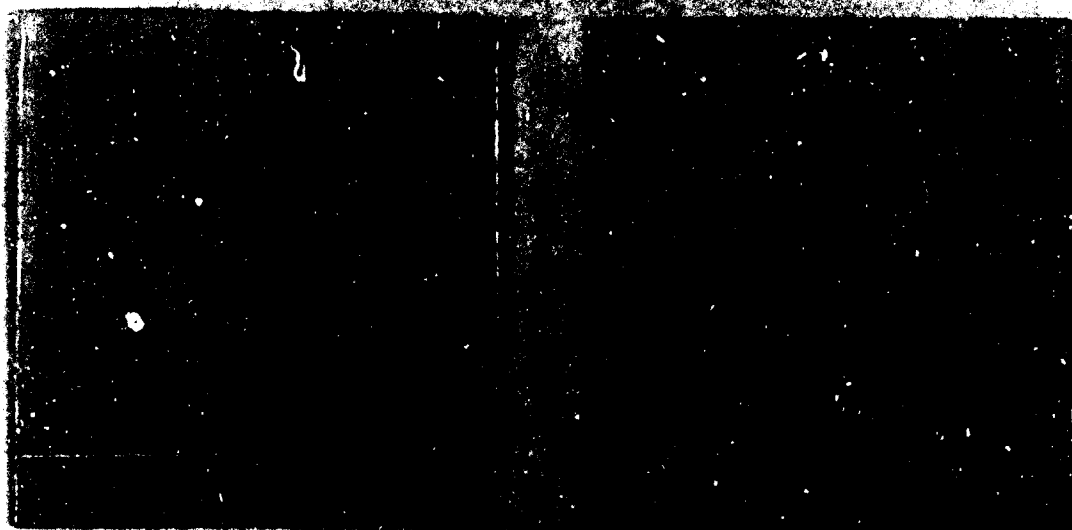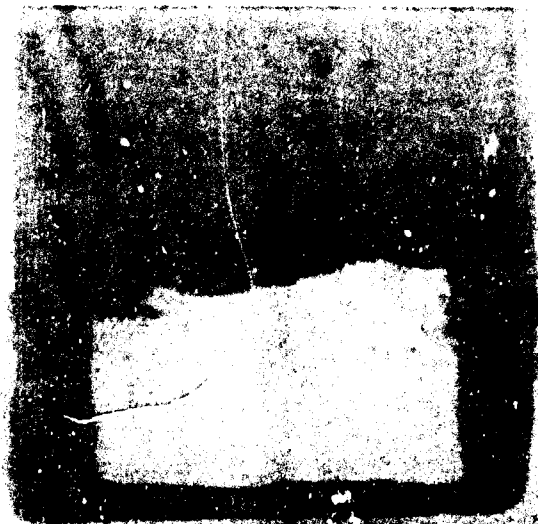

15




16

TIN COATED STEEL PANELS

100% Immersed in 33-1/3% Ethylene Glycol, 66-2/3% water, with various inhibitors



17

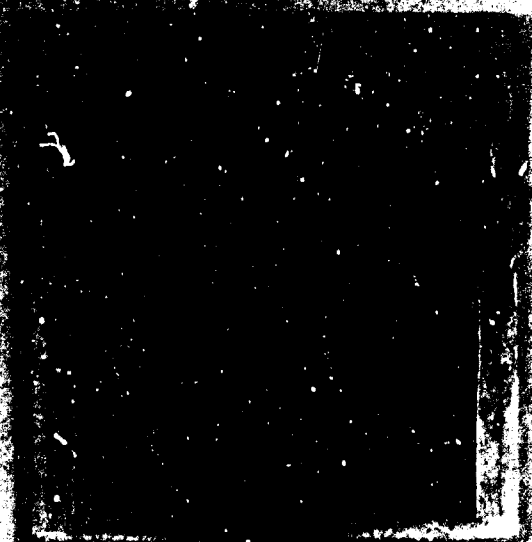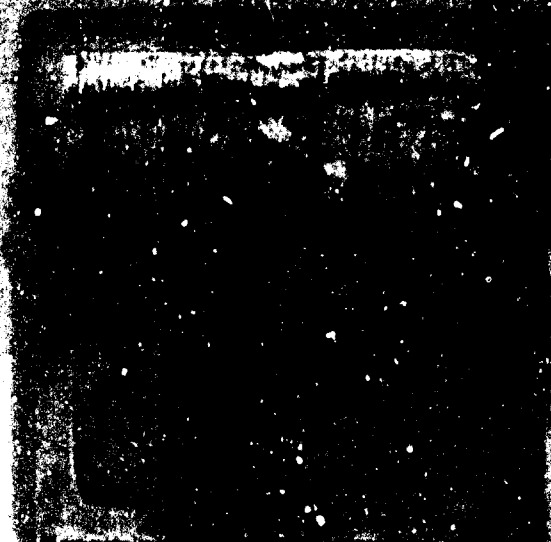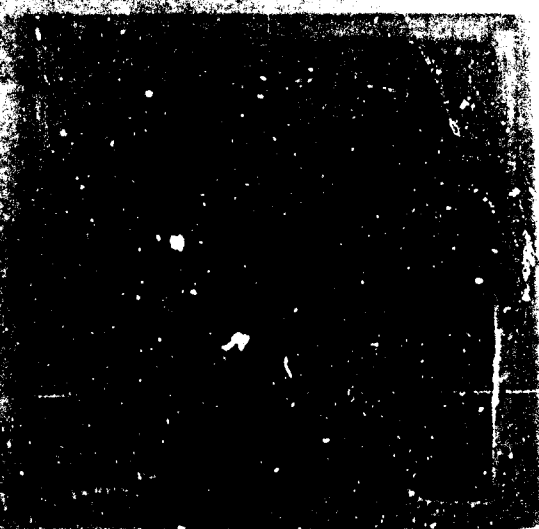

19

20

TIN COATED STEEL PANELS

Panels immersed in 33-1/3% Ethylene Glycol, 66-2/3% water, with various inhibitors





23

24

TIN COATED STEEL PANELS

Panels immersed in 33-1/3% Ethylene Glycol, 66-2/3% water, with various inhibitors

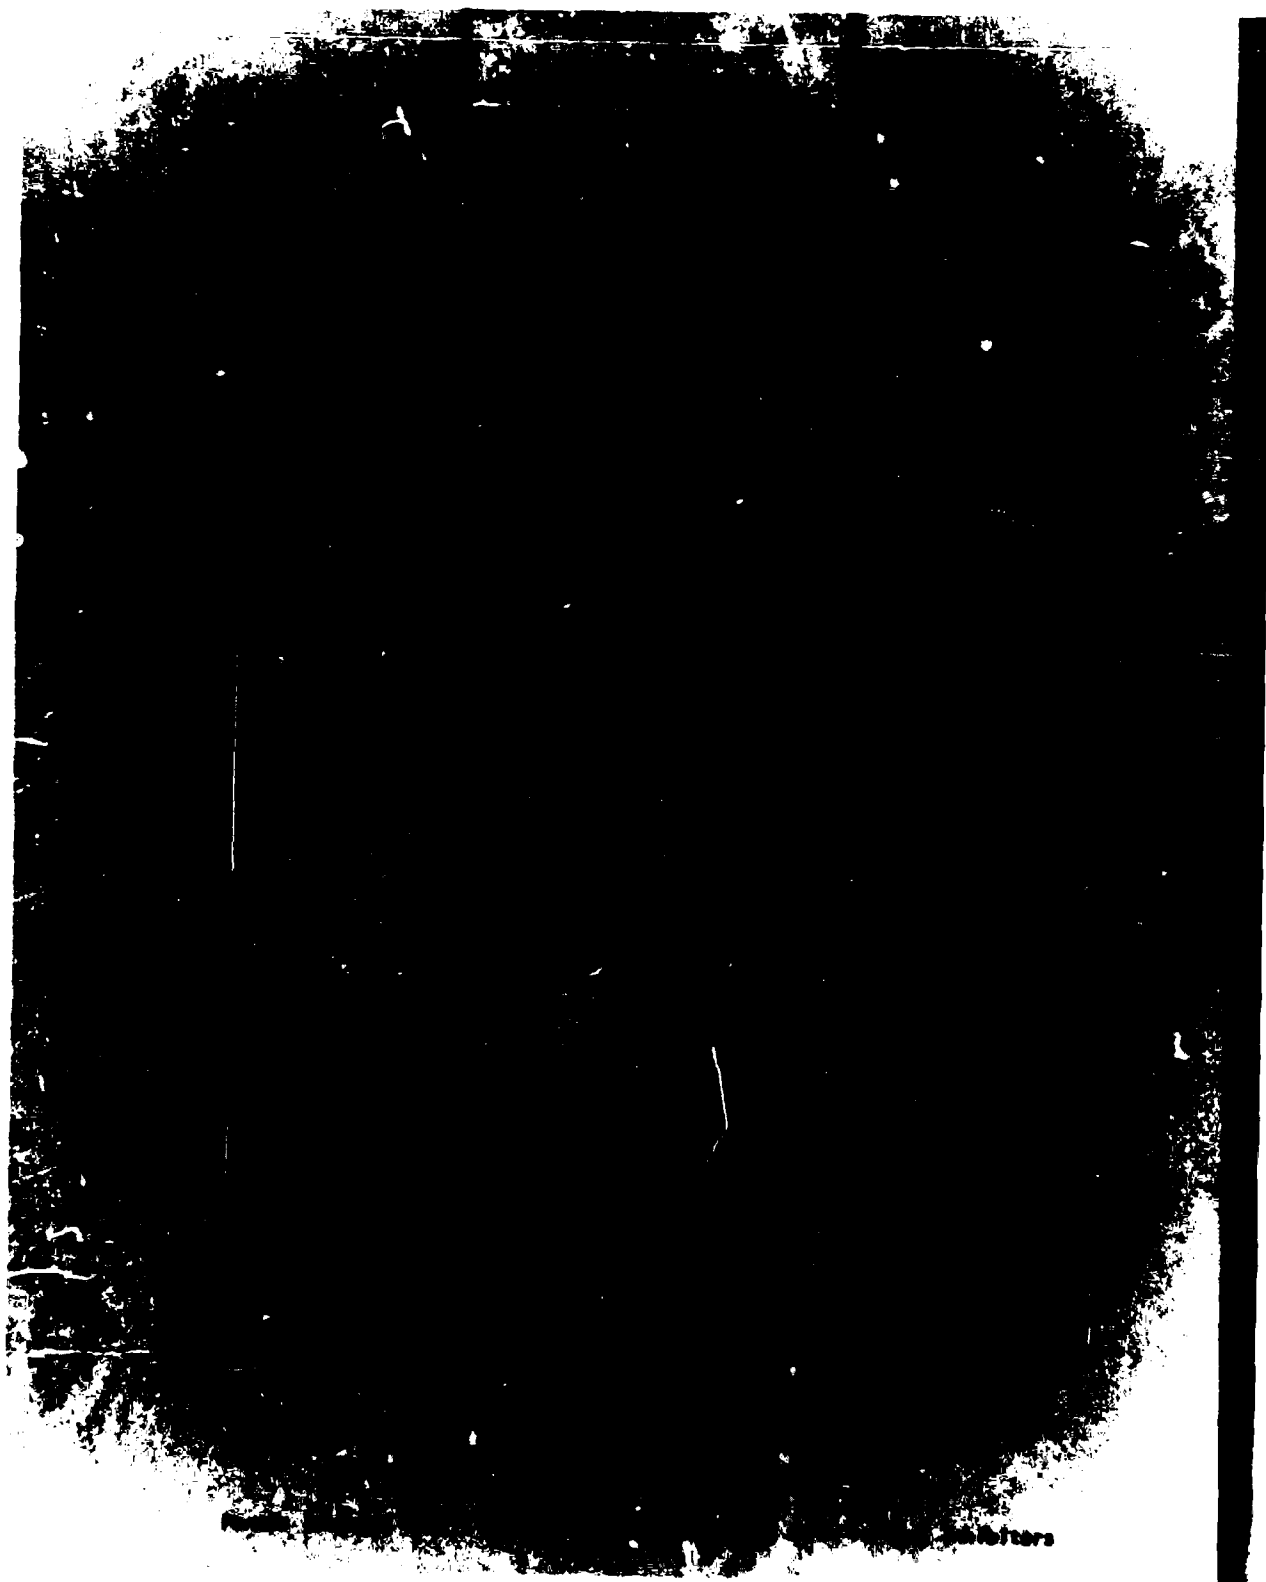

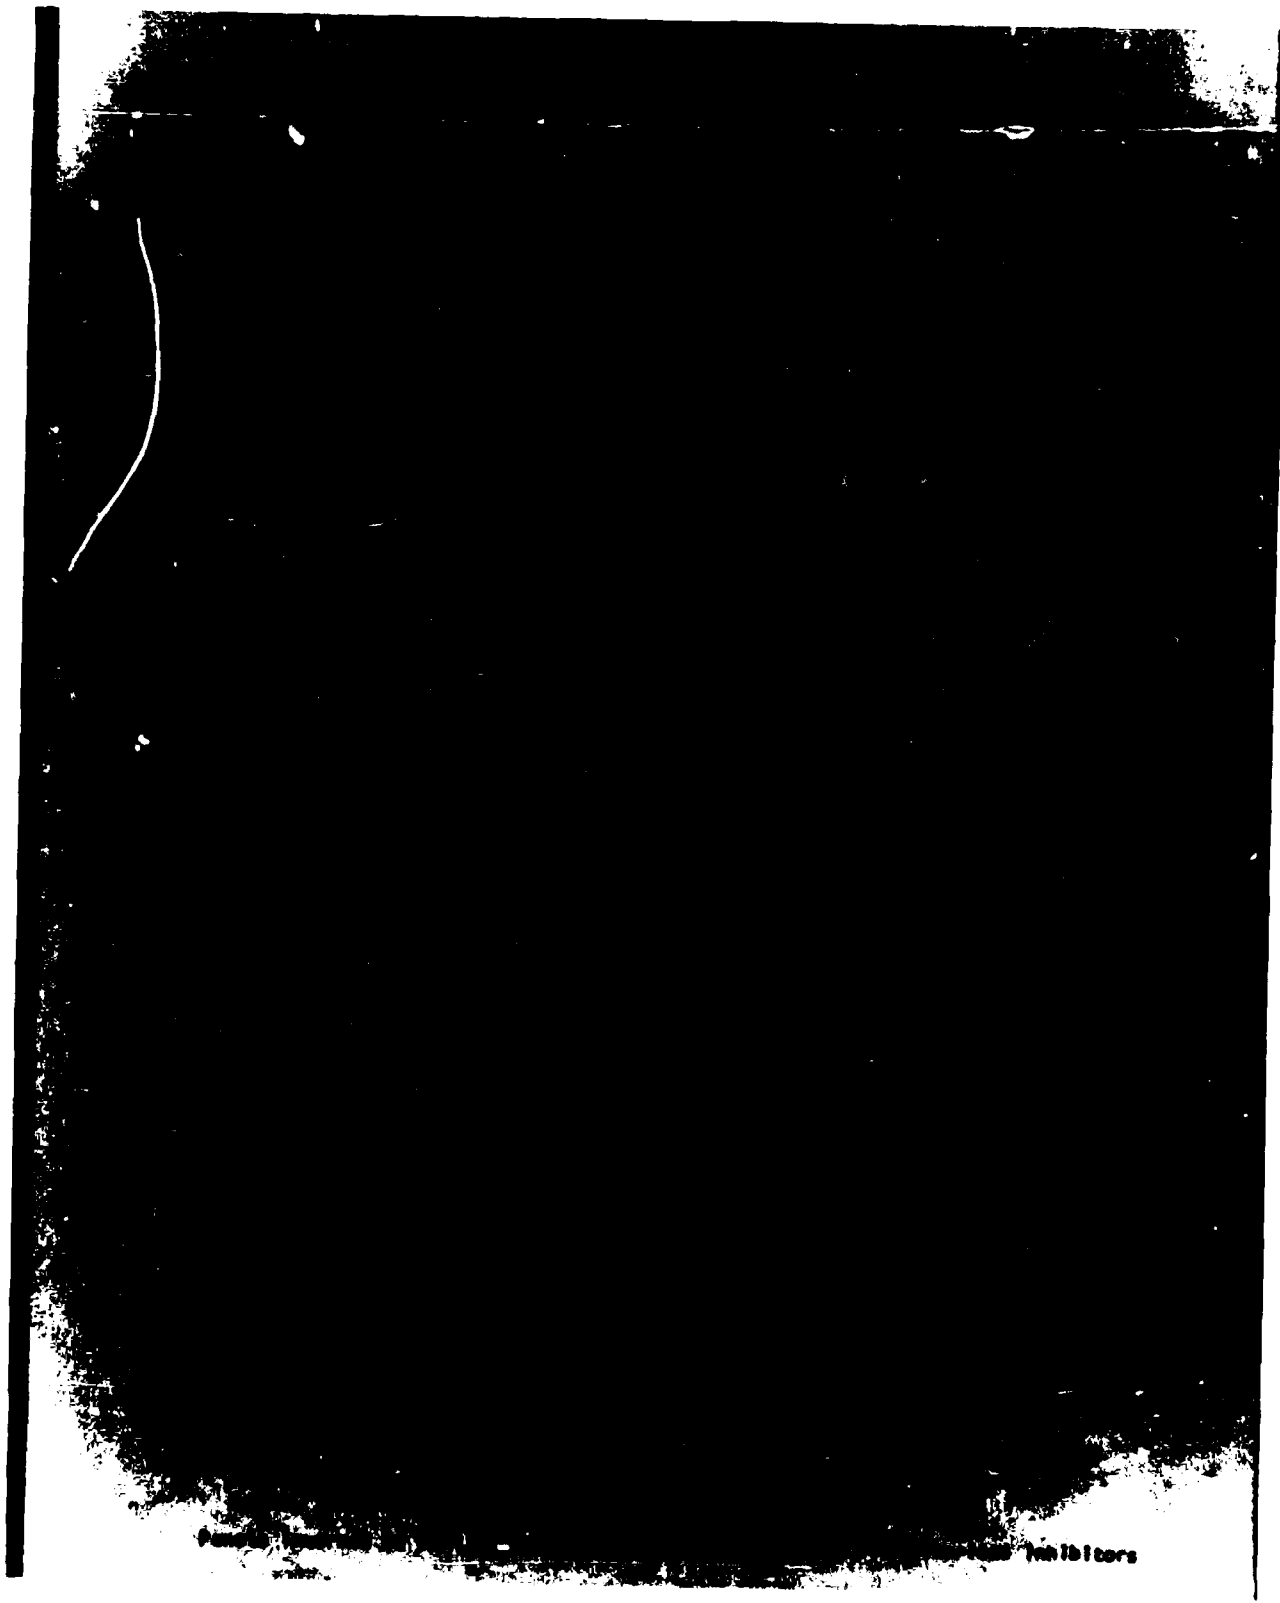

Copyright © 1995 by the American Psychological Association 0893-3200/95 \$12.00 DOI: 10.1037/0893-3200.10.4.511



DOCUMENT CONTROL DATA - R&D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author) U.S. Army Aberdeen Research & Development Center Coating & Chemical Laboratory Aberdeen Proving Ground, Maryland 21005		2a. REPORT SECURITY CLASSIFICATION Unclassified	
		2b. GROUP	
3. REPORT TITLE STUDY OF LONG TERM PACKAGING OF ETHYLENE GLYCOL ANTIFREEZE			
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Final Report			
5. AUTHOR(S) (Last name, first name, initial) Conley, James H.			
6. REPORT DATE July 1969	7a. TOTAL NO. OF PAGES 24	7b. NO. OF REFS 6	
8a. CONTRACT OR GRANT NO. AMCMS Code No. 5025.11.803	9a. ORIGINATOR'S REPORT NUMBER(S) CCL #268		
b. PROJECT NO. 1G062105A109	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)		
d.			
10. AVAILABILITY LIMITATION NOTICES This document has been approved for public release and sale; its distribution is unlimited. Qualified requesters may obtain copies of this report from Defense Documentation Center.			
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY U.S. Army Materiel Command Washington, D. C. 20315	
13. ABSTRACT The object of this study was to investigate conditions which would effect long term packaging of ethylene glycol antifreeze. Factors investigated were pH, dilution, different inhibitor systems and different metals. Aluminum and tin-coated steel panels were partially immersed in ethylene glycol solutions contained in test jars at room temperatures for a period of ten years. Inhibitors used in this study included borax, borax-glycol condensate, mercaptobenzothiazole, and the sodium salt of mercaptobenzothiazole. pH values ranging from 6 to 10.6 were used. Test solutions contained 0%, 3% and 66-2/3% water. No system was adequate for 10 years storage. All systems exhibited corrosion in the liquid phase and/or the vapor phase.			

Antifreeze Packaging
Inhibited Ethylene Glycol
Corrosion
Mercaptobenzothiazole
Borax-Glycol Condensate

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.

UNCLASSIFIED
Security Classification